



## Photocatalytic Degradation of Commercially Important Diazo dye Reactive Brown 10 by $\text{CeFeO}_3$

Vinod Kumar Mehta and B.V.Kabra

Department of Chemistry, M.L.V. Govt. College, Bhilwara, Rajasthan, India

Corresponding author E-mail: [vinod.mehta.1410@gmail.com](mailto:vinod.mehta.1410@gmail.com)

### Abstract

In present work efficiency of  $\text{CeFeO}_3$  as photocatalyst for degradation of Reactive Brown 10 was studied. Photocatalytic bleaching of Reactive Brown 10 was observed spectrophotometrically. The influence of variation of different reaction parameters such as concentration of dye; pH and amount of photo catalyst were observed. The optimum conditions for photocatalytic degradation have been established. The optimum conditions for the degradation of Reactive Brown 10 dye have been found as dye concentration  $3 \times 10^{-5} \text{M}$ ,  $\text{pH}=8.0$  and  $0.06 \text{ g}/100 \text{ ml}$  catalyst dose. The kinetics of degradation of the dye follows first order kinetics. A tentative mechanism for degradation of dye by  $\text{CeFeO}_3$  has been proposed. The presence of hydroxyl radical as an active oxidising species has been confirmed.

**Keywords:** Reactive Brown 10, Photocatalyst, Photocatalytic bleaching

### Introduction

Azo dyes are versatile class of colored organic compounds, which are characterized by the presence of one or more azo bonds ( $-\text{N}=\text{N}-$ ). These are widely used in number of industries such as textile dyeing, food, leather, additive, cosmetic, paper, pharmaceutical industries etc. (Gogate and Pandit, 2004; Pignatello *et al.*, 2006).


During dye production and textile manufacturing processes, a large quantity of waste water containing dyestuffs with intensive color and toxicity are introduced into the aquatic systems (Bhatt, *et al.*, 2004). These dyes do not decompose rapidly through natural processes and are resistant to aerobic degradation. The azo linkage is reduced to aromatic amines under anaerobic conditions that can be toxic and potentially carcinogenic (Kondo *et al.*, 2002; Anjaneyulu *et al.*, 2005; Benatti *et al.*, 2006).

It is necessary to find an effective method of wastewater treatment in order to remove color from effluents. A number of physical and chemical techniques has been reported for the removal of dye compounds such as adsorption on activated carbon (Alnuaimi *et al.*, 2007), biodegradation (Selvan *et al.*, 2005), ozonation (Fernandez *et al.*, 2004) and advanced oxidation processes (AOPs) such as Fenton and photo-Fenton catalytic reactions (Domiguez *et al.*, 2005; Guivarch *et al.*, 2003), H<sub>2</sub>O<sub>2</sub>/UV processes (Jojwiak *et al.*, 2007) and semiconductor photocatalysis (Rodriguez *et al.*, 2006; Dutta *et al.*, 2003; Catastini *et al.*, 2004).

Advance oxidation processes are the methods in which very reactive species such as hydroxyl radicals ( $\cdot\text{OH}$ ) are produced. The hydroxyl radical is a powerful oxidant that can rapidly and non-selectively oxidize organic contaminants into carbon dioxide and water (Liou *et al.*, 2003; Oh *et al.*, 2003), so it is able to degrade pollutants effectively (Miller *et al.*, 2003; Liou *et al.*, 2004). Among the AOPs heterogeneous photocatalytic oxidation using CeFeO<sub>3</sub> as photocatalyst has been extensively studied. CeFeO<sub>3</sub> is very effective, relatively inexpensive, easily available and chemically stable photocatalyst. The appropriate illumination of these particles produces excited-state high energetic electron and hole pairs ( $e^-/h^+$ ). These pairs are able to initiate a wide range of chemical reactions that may lead to complete mineralization of organic and inorganic pollutants (De *et al.*, 2005; Stapleton *et al.*, 2006; Legrini *et al.*, 2008; Hoffmann *et al.*, 2009).

## Materials and Methods

All reagents of analytic grade were used as received without further purification. The CeFeO<sub>3</sub> nanoparticles were synthesized by co-precipitation followed by calcinations. The synthesized particles were characterized and used as photocatalyst for degradation of an azo dye Reactive Brown 10, Metal nitrates of Cerium and iron were used for synthesis of photocatalyst because Nitrate group act as oxidizing agent and have high solubility in water.

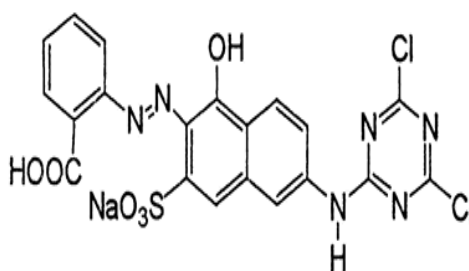

**Fig. I: Chemical Structure of Reactive Brown 10** (C<sub>20</sub>H<sub>11</sub>Cl<sub>2</sub>N<sub>6</sub>NaO<sub>6</sub>S)  
Molecular Weight: 557.30  $\lambda_{\text{max}}$ : 620 nm

## Method

The cerium iron oxide particles were synthesized by precipitation of metal nitrates of cerium and iron. The  $\text{Ce}(\text{NO}_3)_3 \cdot 6\text{H}_2\text{O}$  and  $\text{Fe}(\text{NO}_3)_3 \cdot 9\text{H}_2\text{O}$  were respectively dissolved in distilled water at room temperature to produce 0.1 M aqueous solution. The ternary oxide  $\text{CeFeO}_3$  was prepared by adding 1 M NaOH drop wise to the solution of  $\text{Ce}(\text{NO}_3)_3 \cdot 6\text{H}_2\text{O}$  and  $\text{Fe}(\text{NO}_3)_3 \cdot 9\text{H}_2\text{O}$  with continuous stirring. The pH of solution was monitored and complete precipitation was obtained at pH 9. The precipitate was filtered and washed. This precipitate was kept in oven at  $120^\circ\text{C}$  for drying. After drying it was grounded in mortar and pestles. Subsequently, calcinations were performed. The powder was calcined at  $600^\circ\text{C}$  for 5 hours.

## Characterization

Power XRD was performed with Rigaku Micromax-007 HF instrument using Cu K $\alpha$  ( $\lambda=1.54\text{\AA}$ ) radiation. The stoichiometry of The  $\text{CeFeO}_3$  has been established with the help of published diffraction data file JCPDS. All peaks can be indexed to the typical perovskite structure. (JCPDS card 22-0166).

## Experimental Procedure


The degradation of Reactive Brown 10 was studied in presence of photocatalyst  $\text{CeFeO}_3$  at different pH level, catalyst loading and dye concentration.  $1 \times 10^{-3}$  M dye solution was prepared by dissolving 0.557 g of dye in 1000 ml of distilled water. The initial absorbance of dye solution was observed with the help of UV-VIS spectrophotometer (Shimadzu, UV-700, Pharmaspec). The maximum absorbance Value 0.652 was recorded at 620 nm ( $\lambda_{\text{max}}$ ). The reaction mixture was prepared by taking 3 ml of dye solution ( $1 \times 10^{-3}$  M), 0.06 g of Cerium iron oxide in a round bottom flask. The total volume of the reaction mixture was made 100 ml by adding double distilled water. The concentration of dye in the reaction mixture was  $3.0 \times 10^{-5}$  M. To carry out the photobleaching, the reaction mixture was irradiated under light source (2 x 200 W Tungsten lamps). Water filters were used to cut off thermal radiation. The pH of the solution was measured by pH meter (Systronics, 106). The progress of the reaction was observed at definite time intervals by measuring absorbance using spectrophotometer at 620 nm.

The rate of decrease of colour with time was continuously monitored. After complete mineralization, the presence of  $\text{NO}_2^-$ ,  $\text{NO}_3^-$  ions and evolution of  $\text{CO}_2$  were tested by standard procedures. The pH of the reaction was adjusted by adding 0.1 M NaOH and 0.1M HCl solutions.

## Results and Discussion

The synthesized  $\text{CeFeO}_3$  Was analyzed for its composition and crystal structure by powder XRD. The XRD pattern of  $\text{CeFeO}_3$  is shown in figure II. The graph has been plotted between intensity and  $2\theta$  value (in degrees). All peaks can be indexed to typical perovskite structure (JCPDS Card 22-0166). Any peak of impurity was not observed. The sharp and narrow peaks indicate high crystallization of prepared  $\text{CeFeO}_3$ .

**Fig. II XRD synthesized  $\text{CeFeO}_3$**

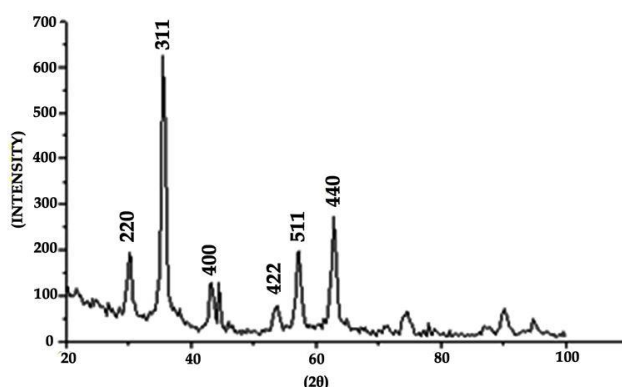

The result of photocatalytic bleaching of Reactive Brown 10 are given in table 1.

**Table: 1 TYPICAL RUN**

[Reactive Brown 10] =  $3 \times 10^{-5}$  M

Amount of catalyst 0.06 g/100 ml

$\lambda_{\text{max}} = 620$  nm

pH = 7.5

**A typical run of photocatalytic degradation of Reactive Brown 10**

Time (min)	Abs	1+log abs
0	0.652	0.8142
20	0.600	0.7782
40	0.555	0.7443
60	0.516	0.7126
80	0.477	0.6785
100	0.441	0.6444
120	0.410	0.6128
140	0.378	0.5775
160	0.352	0.5465

It was observed that absorbance decreases with the increase in time of irradiation indicating that the dye is on degraded irradiation in presence of photocatalyst  $\text{CeFeO}_3$ . A graph between  $1 + \log \text{abs}$  and time has been plotted. The linearity of the plot indicates that the photocatalytic

bleaching of Reactive Brown 10 follows a first order kinetics. The rate constant of this photobleaching process was determined using the expression.


$$\text{Rate constant (k)} = 2.303 \times \text{Slope} = 6.51 \times 10^{-5} \text{ sec}^{-1}$$

The effect of variation in various reaction parameters has been studied e.g. pH, concentration of the dye, amount of photocatalyst. Control experiments (in absence of photocatalyst, light) confirm the necessity of photocatalyst and light for the photobleaching of dye.

#### Effect of amount of catalyst on the rate of decolorization of the dye:

Keeping all other factors identical, the concentration of catalyst was changed and its effect on the rate of photochemical degradation was observed.

**Fig. III: Effect of amount of catalyst on rate of decolorization of Reactive Brown 10I**

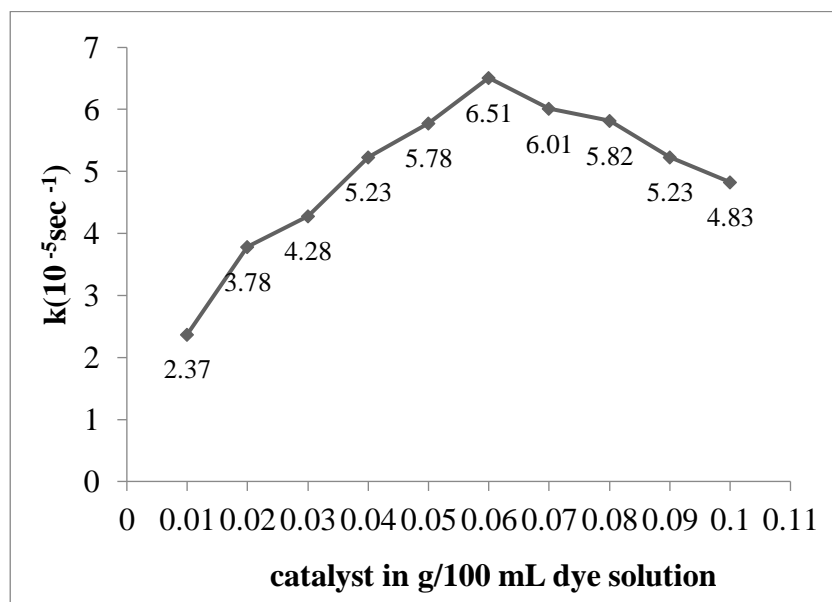

#### A graph showing effect of variation in amount catalyst on photodegradation of RB 10 by CeFeO<sub>3</sub>


The result reveals that the rate of photobleaching of dye increases with the increase in the amount of catalyst CeFeO<sub>3</sub> up to 0.06g/ 100 ml of dye solution and beyond this the rate of reaction becomes almost constant. The increase in amount of catalyst in the reaction mixture is accompanied by enhanced generation of OH<sup>•</sup> radicals as the surface area of catalyst increase OH<sup>•</sup> radical is an extremely strong oxidant which degrade the dye molecule. Further increase in photocatalyst above 0.06 g has negligible effect on dye degradation. The amount of catalyst

increases with same concentration of dye, further dye molecules are not available for adsorption. Therefore, additional catalyst particles are not involved in catalytic activity and rate of reaction is constant.

#### Effect of variation in hydrogen ion concentration on the rate of decolorization of the dye:

In this study, photodegradation was performed at different pH from 5.5 to 10.0. It has been observed that pH 8 is the optimal pH for degradation of Reactive Brown 10. Hence all subsequent experiments were carried out at pH 8. After pH 8 there is an adverse effect on the rate of reaction increasing pH further. The observation can be explained on the basis that as pH of solution increases more OH ions are available. These OH will generate OH radicals by combining with the hole semiconductor photocatalyst. The pH of reaction mixture has a significant effect on the surface properties of  $\text{CeFeO}_3$  catalyst hence photocatalytic activity.

**Fig. IV: Effect of pH on rate of decolorization of Reactive Brown 10**

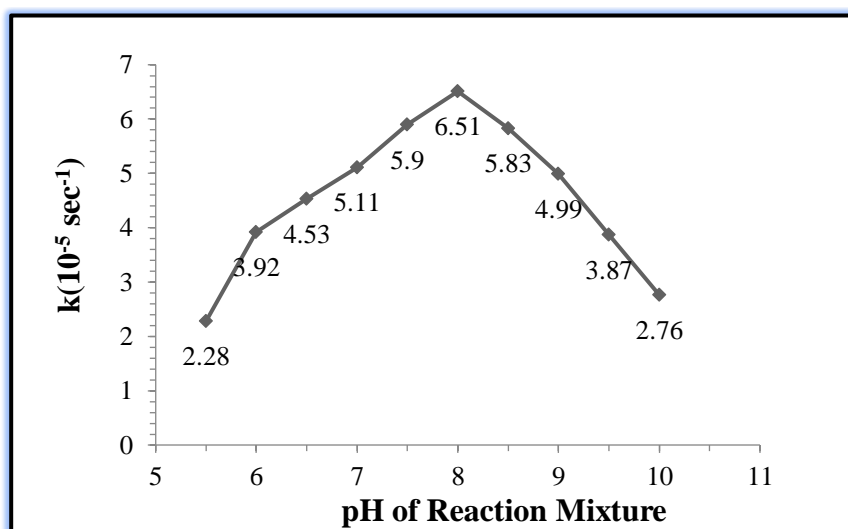


#### Effect of variation in dye concentration on the rate of decolorization of the dye:

The Effect of dye concentration on the degradation of Reactive brown 10 was studied at different concentrations varying from  $1.0 \times 10^{-5}$  to  $5.5 \times 10^{-5}$  keeping all other factors identical. The result reveals that initially rate of reaction increase with Increase in concentration of dye. The highest rate of reaction was Observed for  $3.0 \times 10^{-5}$  M dye solution. Further the rate of photobleaching of dye decreases with the increase in the concentration of the dye. The reason behind it is that the increase in the initial concentration of the dye lies in consistency of the hydroxyl radicals concentration for all the dye molecules and therefore the rate of



decolorization increase. Dye molecules adsorb on Catalyst surface and degradation occurs. On increasing the concentration of dye, keeping catalyst dose constant, catalyst surface gets saturated. Simultaneously intense colour of dye does not permits light to reach photocatalyst. As result rate of degradation decrease.

**Fig. V: Effect of dye concentration on rate of decolorization of Reactive Brown 10**




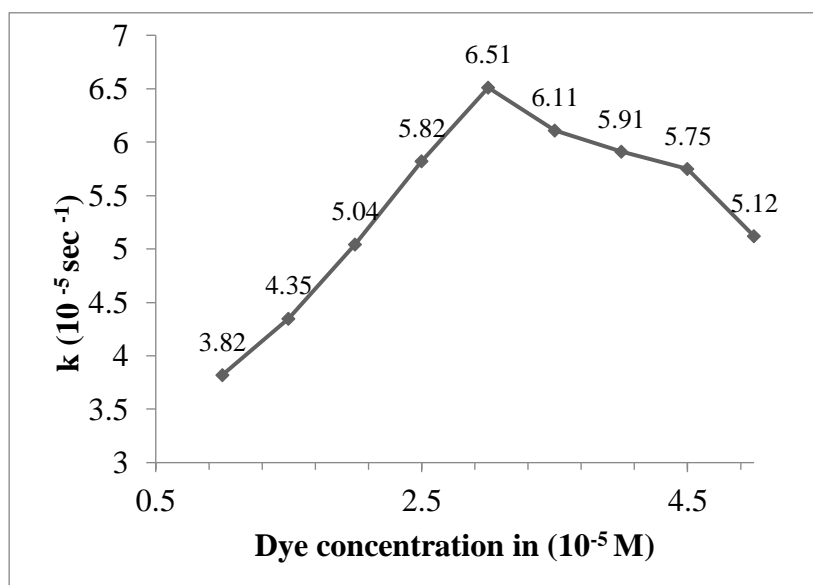


### Mechanism


Photocatalysis is initiated by absorption of photon with energy equal or greater than the band gap of semiconductor  $\text{CeFeO}_3$ .  $\text{CeFeO}_3$  absorbs light in visible region. Electrons from valence band shift into conduction band. Thus, a hole ( $h^+$ ) is generated in valence band. The photogenerated hole is strong oxidizing agent and electron in conduction band acts as reducing agent.




These electron hole pairs migrate to catalyst surface where radicals are generated.



$\text{OH}^\bullet$  (hydroxyl radical)  $\text{O}_2^{\bullet-}$  (superoxide radical)  $\text{HO}_2^\bullet$  (peroxide radical) are strong oxidizing species and react with dye molecules to oxidize them. Simultaneously a dye molecule absorb radiation of suitable energy and get excited to its first singlet state followed by intersystem crossing to triplet state.



ISC



The participation of  $\text{OH}^\bullet$  was confirmed using scavenger 2-propanol. The rate of reaction was drastically reduced in the presence of 2-propanol. The formation of  $\text{CO}_2$ ,  $\text{NO}_3^-$ ,  $\text{NO}_2^-$  in degraded reaction mixture shows there is a complete mineralization in this process. The end products are harmless to the environment.

### Conclusion

Cerium iron oxide is effectively utilized as photocatalyst for degradation of textile dye Reactive Brown 10 in aqueous solution. It is found that degradation is dependent on various reaction parameters web as pH, dye concentration, amount of catalyst. The optimum condition for degradation is at pH 8, 0.06 g  $\text{CeFeO}_3$ / 100 ml dye solution and  $3 \times 10^{-5}$  M dye concentration. Overall findings suggest need to exploit this photocatalyst for wastewater treatment of textile effluent.

### Acknowledgements

The authors are thankful to Dr.Kumod Singh Meena (M.L.V. Govt. College, Bhilwara) for continuous encouragement in accomplishing this work. We are also grateful to Dr. V.K.Vaidya, Dr.Avnish Sharma, Dr.Shelendra Jain, Department of Chemistry, M.L.V. Govt. College, Bhilwara for their support.

### References

P. R. Gogate, A. B. Pandit: Advances in Environmental Research. 8 (3-4), (2004) 553.



- J. J. Pignatello, E. Oliveros, A. Mackay: *Critical Reviews in Environmental Science and Technology*. 36 (1), (2006) 1.
- N. Bhatt, P. Sharma, R. Chandak and B. V. Kabra: *Orient. J. Chem. Soc.* 20(3), (2004) 609.
- M. M. Kondo, M. A. S. V. Arcos and M. T. Grassi: *Braz. Arch. Biol. Technol.* 45, (2002).
- Y. Anjaneyulu, N. S. Chary. D. S. S. Raj: *Environmental Science and Biotechnology*. 4 (4), (2005) 245.
- C. T. Benatti, C. R. G. Tavares, T. A. Guedes: *Journal of Environmental Management*. 80 (1), (2006) 66.
- M. M. Alnuaimi, M. A. Rauf, S. S. Ashraf: *Dyes and Pigments*. 72 (3), (2007) 367.
- K. Selvan, M. Muruganandham, M. Swaminathan: *Solar energy materials and solar cells*. 89 (1), (2005) 61.
- J. Fernandez, P. Maruthamuthu, A. Renken, J. Kiwi: *Applied Catalysis B: Environmental*. 49 (3), (2004) 207.
- J. R. Domiguez, J. Beltron, O. Rodriguez: *Catalysis Today*. 101 (3- 4), (2005) 389.
- E. Guivarch, C. Lahitte, M. A. Oturan: *Environmental Chemistry Letters*. 1 (1), (2003) 38.
- W. K. Jojwiak, M. Mitros R. Tosik: *Dyes and Pigments*. 74 (1) (2007) 9.
- E. Rodriguez, R. Peche, J. M. Merino, L. M. Camarero: *Environmental Engineering Science*. 24(3), (2006) 363.
- K. Dutta, S. Bhattacharjee, B. Chaudhuri, S. Mukhopadhyay: *J. Environmental Science & Health*. 38 (7), (2003) 1311.
- C. Catastini, S. Rafqah, G. Mailhot, M. Sarakha: *J. Photochem. Photobiol A: Chem.* 162 (1), (2004) 97.
- M. J. Liou, M. C. Lu, L. N. Chen: *Water Res.* 37 (17), (2003) 3172.
- S. Y. Oh, P. C. Chiu, B. J. Kim, D. K. Cha: *Water Res.* 37(17), (2003) 4275.
- C. M. Miller, K. C. Bower, C. Ries: *Environmental Engineering Science*. 20(1), (2003) 65.

M. J. Liou, M. C. Lu, L. N. Chen: Chemosphere. 57 (9), (2004) 1107.

A. K. De, B. K. Dutta, S. Bhattacharjee: Environmental Progress. 25 (1), (2005) 64.

D. R. Stapleton, R. J. Emery., C. Smith: International Journal of Environment and Pollution. 28(1-2), (2006) 87.

O. N. Legrini, Oliveres E and Braun A. M, Photochemical processes for water treatment. Chem Rev. 93: 671–698 (2008).

M. R. Hoffmann, Martin ST and Won Yong Choi, Environmental application of semiconductor photocatalysis. Chem Rev. 95: 69–96 (2009).